

This is the accepted version of the article:

Cuadrado R., Oroszlány L., Deák A., Ostler T.A., Meo A.,
Chepulskii R.V., Apalkov D., Evans R.F.L., Szunyogh L.,
Chantrell R.W.. Site-Resolved Contributions to the
Magnetic-Anisotropy Energy and Complex Spin Structure of
Fe/MgO Sandwiches. *Physical Review Applied*, (2018). 9.
054048: - . 10.1103/PhysRevApplied.9.054048.

Available at:

<https://dx.doi.org/10.1103/PhysRevApplied.9.054048>

Site-resolved contributions to the magnetic anisotropy energy and complex spin structure of Fe/MgO sandwiches

Ramón Cuadrado,^{1, 2, 3,*} László Oroszlány,⁴ András Deák,⁵ Thomas A. Ostler,^{6, 7} Andrea Meo,¹ Roman V. Chepulskii,⁸ Dmytro Apalkov,⁸ Richard F. L. Evans,¹ László Szunyogh,^{5, 9} and Roy W. Chantrell¹

¹*Department of Physics, University of York, York YO10 5DD, United Kingdom*

²*Catalan Institute of Nanoscience and Nanotechnology (ICN2),*

CSIC and BIST, Campus UAB, Bellaterra, 08193 Barcelona, Spain

³*Universitat Autònoma de Barcelona, 08193 Bellaterra (Cerdanyola del Vallès), Spain*

⁴*Department of Physics of Complex Systems, Eötvös University,*

Pázmány Péter sétány 1/A, H-1117 Budapest, Hungary

⁵*Department of Theoretical Physics, Budapest University of Technology and Economics, Budapest, Hungary*

⁶*Faculty of Arts, Computing, Engineering and Sciences,*

Sheffield Hallam University, Howard Street, Sheffield, S1 1WB, UK

⁷*Department of Physics, Université de Liège, B-4000 Liège, Belgium*

⁸*Samsung Electronics, Semiconductor R&D Center (Grandis), San Jose, CA 95134, USA*

⁹*MTA-BME Condensed Matter Research Group, Budapest University of Technology and Economics, Budapest, Hungary*

(Dated: April 26, 2018)

Fe/MgO-based Magnetic Tunnel Junctions (MTJs) are among the most promising candidates for spintronic devices due to their high thermal stability and high tunneling magnetoresistance. Despite its apparent simplicity, the nature of the interactions between the Fe and MgO layers leads to complex finite size effects and temperature dependent magnetic properties which must be carefully controlled for practical applications. In this letter, we investigate the electronic, structural and magnetic properties of MgO/Fe/MgO sandwiches using first principles calculations and atomistic spin modeling based on a fully parameterized spin Hamiltonian. We find a large contribution to the effective interfacial magnetic anisotropy from the two-ion exchange energy. Minimization of the total energy using atomistic simulations shows a surprising spin spiral ground state structure at the interface owing to frustrated ferromagnetic and antiferromagnetic interactions, leading to a reduced Curie temperature and strong layer-wise temperature dependence of the magnetization. The different temperature dependences of the interface and bulk-like layers results in an unexpected non-monotonic temperature variation of the effective magnetic anisotropy energy and temperature-induced spin-reorientation transition to an in-plane magnetization at low temperatures. Our results demonstrate the intrinsic physical complexity of the pure Fe/MgO interface and the role of elevated temperatures providing new insight when interpreting experimental data of nanoscale MTJs.

I. INTRODUCTION

The control of perpendicular magnetocrystalline anisotropy (PMCA) at ferromagnetic transition-metal/insulator interfaces is of paramount importance in the manufacture of spintronic devices, such as perpendicular magnetic tunnel junctions (pMTJs) [1–3] and tunneling anisotropic magnetoresistive (TAMR) systems [4]. Large PMCA can be achieved by fabricating heterostructures including heavy non-magnetic elements with large spin-orbit coupling (SOC) [5], such as Co/Pt or Co/Au [6]. It has been shown that this out-of-plane PMCA enhancement at the interface is due to an increase of orbital moment of Co atoms and strong hybridization of the $3d$ – $5d$ orbitals between the transition metals and the heavy atoms, respectively [6, 12]. Recently it has been demonstrated that other $3d$ transition metal elements show increased PMCA even if their SOC is weak [13–15]. Such is the case of Fe-based thin films at MgO(001) interfaces, where the Fe d_{z^2} –O p_z hybridization at the interfaces results in enhanced PMCA [16].

Using ab-initio calculations Yavorsky and Mertig [17] have

shown the existence of antiferromagnetic Fe/Fe interactions in the Fe plane connected to the MgO. From this they inferred the intriguing possibility of non-collinear magnetic structures but did not determine the ground state spin structure. In addition to the possibility of antiferromagnetic interactions, the ground state spin configuration will be perturbed due to the complex distance dependent exchange interactions which is difficult to quantify in layered systems with broken out of plane translational invariance. Spin fluctuations at elevated temperatures, coupled with the effects of any non-collinearity will naturally lead to complex temperature dependent behavior of the magnetic properties, including the Magnetocrystalline Anisotropy Energy (MAE).

Whilst there are a large number of applications of magnetic/non-magnetic interfaces such as generating Skyrmions [34] or as magnetic tunnel junctions [18] in Magnetic Random Access Memories, the physical properties of such interface systems (including Fe/MgO) are not fully understood. At the electronic level there exists a basic understanding of the interface exchange [17] and anisotropy [21], with very little understanding of thermal and long-range magnetic ordering effects. Detailed understanding of the magnetization dynamics and temperature dependent magnetic properties, particularly that of the magnetization and anisotropy, require a multiscale approach based on atomistic

* ramon.cuadrado@icn2.cat

spin dynamics [22] with ab-initio parameterization. This is especially important given the localization of the magnetic anisotropy at the interface and the possibility of non-collinear spin structures.

In this letter we use a multiscale approach to model the electronic, structural and magnetic properties of the Fe/MgO interface in a sandwich geometry. Our results reveal the role of single-ion and two-ion anisotropy contributions, as well as the long range exchange interactions in the ground state configurations of two different *bcc*–Fe thicknesses sandwiched by two MgO(001) regions: $\cdots \text{MgO}/n_{Fe}\text{Fe}/\text{MgO} \cdots$ [$n_{Fe}=4,8$]. We show that the lack of Fe out-of-plane symmetry and dissimilar in-plane lattice constants compared to the Fe bulk have a drastic effect on the magnetic properties at the Fe/MgO interface, leading to an exchange anisotropy which provides a dominant contribution to the total PMCA. Through atomistic simulations we show that the complex interfacial exchange interactions lead to a spiral ground state spin structure. The temperature dependence of the anisotropy is shown to be non-monotonic, driven by the different temperature dependences of the single-ion and two-ion anisotropies and leads to a significant reduction in the Curie temperature of the system as observed experimentally.

II. DETAILS OF THE CALCULATIONS

We have used the SIESTA software package [24] to obtain the final $\cdots \text{MgO}/n_{Fe}\text{Fe}/\text{MgO} \cdots$ configurations used in the Screened Korringa–Kohn–Rostoker (SKKR) by performing fully ionic conjugate gradient relaxation (see the sec. I of the Supplementary Material [35]). For the calculations we used a high number of MgO planes since the SKKR method requires the system to be considered as an intermediate layer region positioned between two semi-infinite bulk regions. From the fully relaxed geometry, a $9\text{MgO}/n_{Fe}\text{Fe}/9\text{MgO}$ slice is extracted and embedded into the MgO bulk, resulting in an Fe layer sandwiched between two semi-infinite MgO bulk alloys. The presence of the MgO interface leads to enhanced interfacial magnetic and orbital moments, giving total moments of $\sim 2.8 \mu_B$ at the interface compared to $\sim 2.3 \mu_B$ in the middle of the sandwich, as detailed in the Supplementary Information.

The layer-resolved exchange[29] and anisotropy contributions we calculated using the SKKR code (see sec. I of the Supplementary Material for details [35]) allowing for a mapping onto a classical spin Hamiltonian

$$\mathcal{H} = - \sum_{i < j} \mathbf{S}_i \mathcal{J}_{ij} \mathbf{S}_j - \sum_i k_i (\mathbf{S}_i \cdot \mathbf{e})^2 \quad (1)$$

where \mathbf{S}_i is a classical unit vector parallel to the magnetization at site i , \mathcal{J}_{ij} is the exchange interaction tensor between sites i and j , and the last term represents the on-site anisotropy, with the anisotropy constant k_i and \mathbf{e} the easy axis direction. Within the SKKR formalism, the total magnetic anisotropy energy (MAE), defined as the total energy difference between hard and easy magnetization directions, can be resolved into

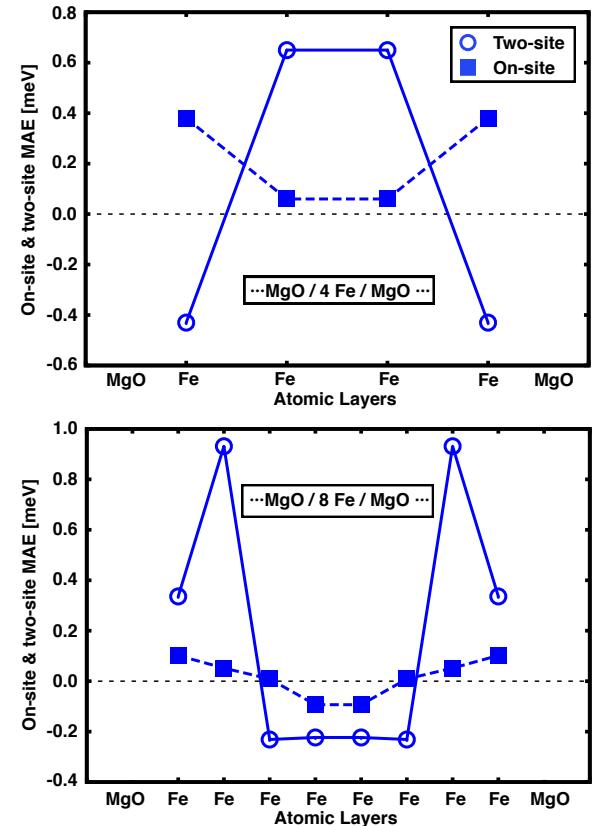


FIG. 1. (Color online) On-site and two-site MAE contributions for $\cdots \text{MgO}/n_{Fe}\text{Fe}/\text{MgO} \cdots$ [$n_{Fe}=4,8$].

layer-wise contributions K_l

$$K = \sum_l K_l = K_{\text{on-site}} + K_{\text{two-site}}, \quad (2)$$

where $K_{\text{on-site}} = \sum_l k_l$ and $K_{\text{two-site}}$ is given an exchange anisotropy by the difference in the zz and xx components of the exchange tensor.

$$K_{\text{two-site}} = - \sum_{i < j} (J_{ij}^{xx} - J_{ij}^{zz}). \quad (3)$$

III. RESULTS

A. Layered resolved magnetic anisotropy

The layer and site-resolved anisotropy contributions are shown in Fig. 1 for (a) $n_{Fe}=4$ and (b) $n_{Fe}=8$ layers. The Mg and O atoms make a negligible contribution to the MAE. At the interface, specifically on the first two Fe planes, the on-site values (blue filled squares) present higher values compared to those in the center for any configuration. In addition, these positive values imply that the Fe atoms contribute to the total MAE with an out-of-plane anisotropy. However, as the thickness increases, the on-site anisotropy in the center becomes more complex and for $n_{Fe}=8$ the easy axis lies in-plane.

For four Fe planes ($n_{Fe}=4$), the on-site contribution to the MAE is four times larger than that of the $n_{Fe}=8$ case, which we attribute to the enhanced orbital magnetic moment from the small number of Fe planes in the system. The thickness dependence of the two-site anisotropy is more complicated, showing a sign change for the interface layer between $n_{Fe}=4$ and $n_{Fe}=8$ layers and also the appearance of a preferred in-plane orientation of the magnetization at the center of the $n_{Fe}=8$ layer sandwich. In all cases the two-ion contributions to the MAE are seen to be dominant. Due to the different temperature dependent scalings of single-ion and two-ion anisotropies [30] with the magnetization (m^3 and m^2 at low temperature, respectively) their relative magnitudes determine the overall temperature dependence of the PMCA. Most *ab-initio* calculations do not distinguish the origin of the PMCA, only its magnitude and therefore simple assumptions for the macroscopic temperature dependence of the anisotropy based on Callen-Callen theory [31] are likely to be erroneous. It is worth mentioning that other theoretical works have been performed in order to gain more insight into the nature of PMCA at Fe/MgO interfaces [21] and at CoFe/MgO interfaces for different compositions [32]. In good agreement with our results (see Fig. 1), both works conclude that the main contributions to the anisotropy energy come from the two ferromagnetic layers closest to the interface. Zhang et al. [32] found that the PMCA at $Co_{1-x}Fe_x/MgO$ interfaces strongly depends on the composition of CoFe, decreasing with increasing Co concentration. Moreover, at a certain x value there is a transition from positive to negative MCA. Hallal and coworkers [21] found that, beside the main interfacial contribution, the anisotropy energy propagates into the ferromagnetic bulk, showing an attenuating oscillatory behavior. In the present work (see the entry for $n_{Fe}=8$ in Fig. 1) we also clearly observe this oscillatory behavior of the anisotropy energy.

B. Exchange magnetic interactions

In addition to site-resolved anisotropies, we have studied the effect of the MgO/Fe interface on the interatomic exchange interactions. To aid analysis, we consider the trace of the exchange tensor $J_{ij}^{iso} = \frac{1}{3}Tr \mathcal{J}_{ij}$ which forms the dominant part of the exchange energy. The range dependence of the exchange energy for the $n_{Fe}=8$ system for different layers is shown in Fig. 2(a). As is commonly observed, the exchange interactions are long-ranged and oscillatory in nature but also dominated by interactions with the nearest magnetic moments and decay rapidly with interatomic distance. The leading terms for all layers are ferromagnetic, leading to a general expectation of ferromagnetic ordering as would be expected for Fe. For bulk Fe, the exchange, as also shown by Yavorsky et. al. [17]) shows antiferromagnetic contributions with the behavior becoming oscillatory after a couple of lattice spacings. However, in the Fe/MgO interface system, the exchange remains antiferromagnetic for interactions out to a much longer range. To better resolve the origin of the ferromagnetic interactions we have separated the exchange interactions by layer in Fig. 2(b). This separation clearly shows that

the large antiferromagnetic interactions in the interface layer occur between atoms in the same plane. For the smaller $n_{Fe}=4$ system, the nearest neighbor interactions are similar, while the in-plane antiferromagnetic interactions are 40 meV larger, likely leading to a qualitatively different magnetic structure. In general, the isotropic Fe exchange at the interfaces for any n_{Fe} behaves in the same way, i.e., from the third Fe layer the magnetic behavior is similar to any Fe atom within the bulk and the main differences in the magnetic properties arise at the interface.

C. Mesoscopic temperature dependence

While the *ab-initio* calculations give information about the nature of the interactions in the system, their complex nature makes it difficult to draw clear conclusions about the macroscopic magnetic properties of the system as the ground state is governed by the balance of the whole set of interactions. The *ab-initio* calculated Hamiltonian can then be used to determine the ground state structure at elevated temperatures through atomistic spin modeling. The calculations utilize the VAMPIRE software package [23, 26] considering a $10\text{ nm} \times 10\text{ nm} \times 8$ monolayer (ML) system of Heisenberg spins with periodic boundary conditions in the plane. We consider the

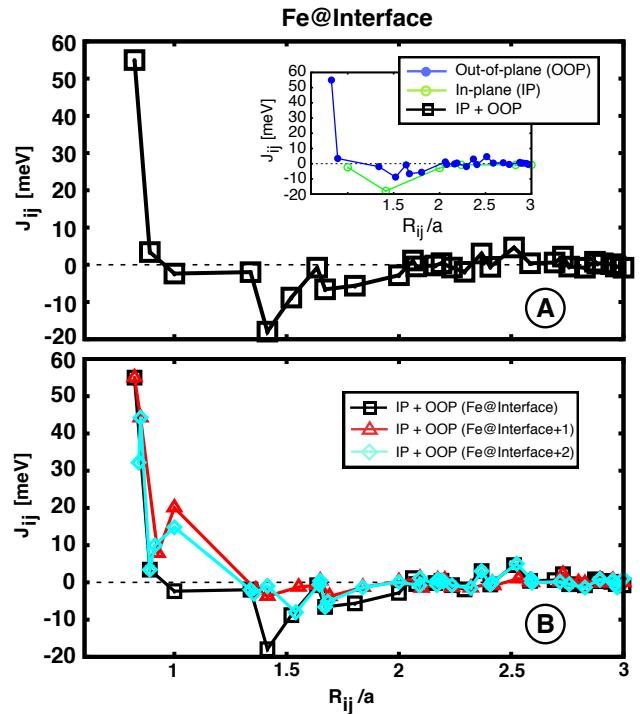


FIG. 2. (Color online) (A) Fe-Fe isotropic magnetic exchange interactions as a function of the neighbor distances for an Fe atom located @Interface of the ...MgO/8Fe/MgO... configuration. Inset shows the intralayer and interlayer isotropic exchange contributions. (B) Fe-Fe isotropic magnetic exchange interactions for Fe@Interface and @Interface+1/2, black squares, red triangles and turquoise diamonds, respectively. The solid lines are guides for the eye.

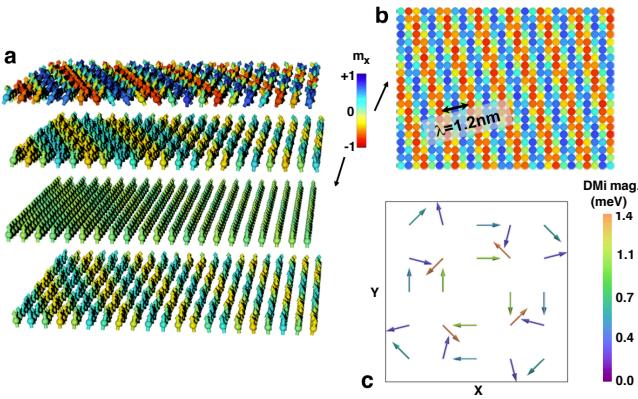


FIG. 3. (Color online) Perspective (a) and top (b) view of the simulated ground state spin structure at the $n_{Fe}=8$ -Fe/MgO interface for $n_{Fe}=8$, leading to a near-ferromagnetic state in the centre of the sandwich. The coloring indicates the x -component of the magnetization (blue for $+x$, red for $-x$ and green for $x=0$). The atomic moments form a non-collinear configuration with wavelength $\lambda = 1.2 \text{ nm}$ and angle between spins not larger than 45° in the perpendicular direction. (c) Plot of Dzyaloshinsky-Moriya interactions (DMi), which lay in the x - y plane solely, for the top layer of the same system.

full exchange tensor of over 2000 interactions per spin, localized anisotropy and magnetic moments in the simulations. Metropolis and constrained [30] variants of Monte Carlo algorithms are used to determine the ground state spin configurations in a plane-by-plane manner as well as the Curie temperature and temperature dependent anisotropy.

A visualization of the final magnetic ground state for $n_{Fe}=8$ is shown in Fig. 3(a) and (b). In (a) the top plane represents Fe at the MgO interface where a spin spiral ground state appears due to the frustration between ferromagnetic and antiferromagnetic interactions and the appearance of Dzyaloshinskii-Moriya interactions (DMi) [10, 11] at interface due to broken inversion symmetry. The temperature dependence of the spin spiral state is discussed in section IV of the Supplementary Material [35]. Interestingly the orientation of the spiral is at $\sim 16.4^\circ$ to the x -axis and the spin spiral is confined to the positive z -values ($S_z > 0$). Moving layer-wise towards the center of the sandwich, the spin spiral becomes much less prominent and a ferromagnetic ordering dominates, which confirms that the interfacial antiferromagnetic nearest neighbor interactions and DMi are responsible for the frustrated spin-spiral structure. In fact, such a complex exchange pattern only arises in those layers that are at the interface with MgO. Fig. 3(C) shows the top view of DMi magnitude for the top layer, where a non trivial relationship among the neighbors of both direction and magnitude of DMi it can be seen, and, as they lie in the x - y plane, they can induce non collinear spin configurations.

Using the spin model, we have also investigated the effects of the anisotropy contributions on the overall effective value. The anisotropy is calculated using the constrained Monte Carlo method[30], an approach that allows one to constrain the direction of the magnetization away from the easy axis of the system. The anisotropy shows a surpris-

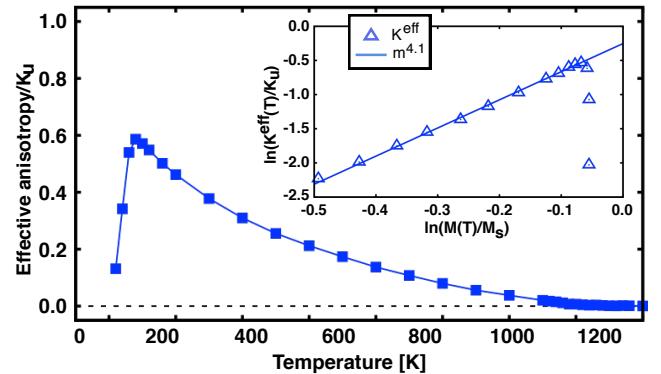


FIG. 4. (Color online) Temperature dependence of the effective anisotropy as function of temperature for the $n_{Fe} = 8$ system; lines provide a guide for the eye. The inset shows the scaling of the anisotropy with the total magnetization; the symbols represent the data and the solid line the fit. The simulations were performed by first equilibrating the system for 10000 Monte Carlo steps at each temperature and angle, and then the average of the torque was calculated over 50000 steps.

ing non-monotonic behavior at low temperatures caused by the spin spiral state. As the temperature driven spin fluctuations increase, this destabilizes the spin spiral ground state leading to an increase in the effective magnetic anisotropy as the magnetic ordering in the interface layer becomes more ferromagnetic-like. Interestingly, the scaling of the effective magnetic anisotropy has an unusual exponent of $k(m) m^{4.1}$, which is expected for neither single-ion (m^3) or two-ion (m^2) anisotropy scaling. We attribute this unusual exponent to the frustrated nature of the exchange interactions at the interface, and so we expect a high exponent for the interface layer and lower for the subsurface layers, which when normalized to the average magnetization gives a higher effective scaling of the anisotropy constant.

IV. CONCLUSIONS

In conclusion, we have presented a fully relativistic electronic structure study of the exchange interactions and the site-resolved MAE of $\cdots \text{MgO}/n_{Fe}\text{Fe}/\text{MgO} \cdots$ [$n_{Fe}=4,8$] sandwiches. Our results reveal a dominant contribution to the MAE from the two-ion exchange anisotropy. Furthermore, we have shown that the competing ferromagnetic and antiferromagnetic interactions at the Fe/MgO interface lead to an overall ferromagnetic ground state but which includes a frustrated spin spiral at the interface, which destabilizes the magnetization of the interfacial layer at elevated temperatures, leading to a reduction of the Curie temperature of the system. The complex equilibrium magnetic properties of this technologically important material are of critical importance to understanding the thermal stability and spin transport properties of nanoscale MTJ devices and can provide key insights into experimental observations.

ACKNOWLEDGEMENTS

The financial support of the Samsung Global MRAM Innovation programme and the European Union under Seventh Framework Programme under Grant No. 281043, FEMTOSPIN is gratefully acknowledged. ICN2 is supported by the Severo Ochoa program from Spanish MINECO (Grant No. SEV-2013-0295). R.C. also acknowledges the funding from the European Unions Horizon 2020 research and innovation program under the Marie Skłodowska-Curie grant agree-

ment no. 665919. T. A. Ostler gratefully acknowledges the Marie Curie incoming BeIPD-COFUND fellowship program at the University of Liège. A.D., L. O. and L.S. acknowledge support by the Hungarian Scientific Research Fund (NKFIH) under projects no. K115575, PD124380, K108676, K115608 and FK124723. L. O. also acknowledges to the National Quantum Technologies Program NKP-375 2017-00001 of the NRDI Office of Hungary. L.O. acknowledges support from the Janos Bolyai Scholarship of the Hungarian Academy of Sciences.

[1] K. Mizunuma, S. Ikeda, J. H. Park, H. Yamamoto, H. Gan, K. Miura, H. Hasegawa, J. Hayakawa, F. Matsukura, and H. Ohno, MgO barrier-perpendicular magnetic tunnel junctions with CoFe/Pd multilayers and ferromagnetic insertion layers, *Appl. Phys. Lett.* **95**, 232516 (2009).

[2] J.-H. Park, C. Park, T. Jeong, M. T. Moneck, N. T. Nufer, and J.-G. Zhu, CoPt multilayer based magnetic tunnel junctions using perpendicular magnetic anisotropy, *J. Appl. Phys.* **103**, 07A917 (2008).

[3] G. Kim, Y. Sakuraba, M. Oogane, Y. Ando, and T. Miyazaki, Tunneling magnetoresistance of magnetic tunnel junctions using perpendicular magnetization L1₀-CoPt electrodes, *Appl. Phys. Lett.* **92**, 172502 (2008).

[4] L. Gao, X. Jiang, S.-H. Yang, J. D. Burton, E. Y. Tsymbal, and Stuart S. P. Parkin, *Phys. Rev. Lett.* **99**, 226602 (2007).

[5] J. Stöhr and H. C. Siegmann, *Magnetism* (Springer, Berlin, 2006).

[6] I. Zutic, J. Fabian, and S. Das Sarma, Spintronics: Fundamentals and applications *Rev. Mod. Phys.* **76**, 323 (2004).

[7] A.I. Liechtenstein, M.I. Katnelson, V.P. Antropov, and V.A. Gubanov, Local spin density functional approach to the theory of exchange interactions in ferromagnetic metals and alloys *J. Magn. Magn. Mater.* **67**, 65 (1987).

[8] J. B. Staunton, L. Szunyogh, A. Buruza, B. L. Gyorffy, S. Osttanin, and L. Uvdardi, Temperature dependence of magnetic anisotropy: An ab initio approach, *Phys. Rev. B* **74**, 144411 (2006).

[9] C. J. Aas, P. J. Hasnip, R. Cuadrado, E. M. Plotnikova, L. Szunyogh, L. Uvdardi, and R. W. Chantrell, Exchange coupling and magnetic anisotropy at Fe/FePt interfaces, *Phys. Rev. B* **88**, 174409 (2013).

[10] I. Dzyaloshinsky, A thermodynamic theory of weak ferromagnetism of antiferromagnetics, *J. Phys. Chem. Solids* **4**, 241 (1958).

[11] T. Moriya, Anisotropic Superexchange Interaction and Weak Ferromagnetism, *Phys. Rev.* **120**, 91 (1960).

[12] D. Weller, Y. Wu, J. Stohr, M. G. Samant, B. D. Hermsmeier, and C. Chappert, Orbital magnetic moments of Co in multilayers with perpendicular magnetic anisotropy, *Phys. Rev. B* **49**, 12888 (1994).

[13] K. Nakamura, T. Akiyama, T. Ito, M. Weinert, and A. J. Freeman, Role of an interfacial FeO layer in the electric-field-driven switching of magnetocrystalline anisotropy at the Fe/MgO interface, *Phys. Rev. B* **81**, 220409(R) (2010).

[14] B. Rodmacq, S. Auffret, B. Dieny, S. Monso, and P. Boyer, Crossovers from in-plane to perpendicular anisotropy in magnetic tunnel junctions as a function of the barrier degree of oxidation, *J. of Appl. Phys.* **93**, 7513 (2003).

[15] M. K. Niranjan, C.-G. Duan, S. S. Jaswal, and E. Y. Tsymbal, Electric field effect on magnetization at the Fe/MgO(001) interface, *Appl. Phys. Lett.* **96**, 222504 (2010).

[16] Kohji Nakamura, Yushi Ikeura, Toru Akiyama, and Tonomori Ito, Giant perpendicular magnetocrystalline anisotropy of 3d transition-metal thin films on MgO, *J. of Appl. Phys.* **117**, 17C731 (2015).

[17] B. Yu. Yavorsky and I. Mertig, Noncollinear interface magnetism and ballistic transport in FeFeOMgOFe tunnel junctions: Ab initio calculations using the KKR method, *Phys. Rev. B* **74**, 174402 (2006).

[18] S. Ikeda, K. Miura, H. Yamamoto, K. Mizunuma, H. D. Gan, M. Endo, S. Kanai, J. Hayakawa, F. Matsukura and H. Ohno, A perpendicular-anisotropy CoFeB-MgO magnetic tunnel junction, *Nature Materials* Vol 9, 721 (2010).

[19] J.C. Slonczewski, Current-driven excitation of magnetic multilayers, *J Magn. Magn. Mater.* **159**, L1 (1996).

[20] L Berger, Emission of spin waves by a magnetic multilayer traversed by a current, *Phys. Rev. B* **54**, 9353 (1996).

[21] A. Hallal, H. X. Yang, B. Dieny, and M. Chshiev, Anatomy of perpendicular magnetic anisotropy in Fe/MgO magnetic tunnel junctions: First-principles insight, *Phys. Rev. B* **88**, 184423 (2013).

[22] N. Kazantseva, D. Hinze, U. Nowak, R. W. Chantrell, U. Atxitia, and O. Chubykalo-Fesenko, Towards multiscale modeling of magnetic materials: Simulations of FePt, *Phys. Rev. B* **77**, 184428 (2008).

[23] R. F. L. Evans, W. J. Fan, P. Chureemart, T. A. Ostler, M. O. A. Ellis, and R. W. Chantrell, Atomistic spin model simulations of magnetic nanomaterials, *J. Phys.: Condens. Matter* **26**, 103202 (2014).

[24] J.M. Soler, E. Artacho, J.D. Gale, A. García, J. Junquera, P. Ordejón and D. Sánchez-Portal, The SIESTA method for ab initio order-N materials simulation, *J. Phys.: Condens. Matter* **14**, 2745, (2002).

[25] J. Zabloudil, R. Hammerling, L. Szunyogh, and P. Weinberger, *Electron Scattering in Solid Matter* (Springer, Berlin, 2005).

[26] <http://vampire.york.ac.uk>

[27] R. Cuadrado and R. W. Chantrell, Interface magnetic moments enhancement of FePt-L1₀/MgO(001): An ab initio study, *Phys. Rev. B* **89**, 094407 (2014).

[28] D. M. Ceperley and B. J. Alder, Ground State of the Electron Gas by a Stochastic Method, *Phys. Rev. Lett.* **45**, 566 (1980).

[29] L. Uvdardi, L. Szunyogh, K. Palotás, and P. Weinberger, First-principles relativistic study of spin waves in thin magnetic films, *Phys. Rev. B* **68**, 104436 (2003).

[30] P. Asselin et al, Constrained Monte Carlo method and calculation of the temperature dependence of magnetic anisotropy,

Phys. Rev. B 82, 054415 (2010)

[31] H.B. Callen and E. Callen, The present status of the temperature dependence of magnetocrystalline anisotropy, and the power law, *J. Phys. Chem. Solids.* **27**, 1271 (1966).

[32] Jia Zhang, Christian Franz, Michael Czerner, and Christian Heiliger, Perpendicular magnetic anisotropy in CoFe/MgO/CoFe magnetic tunnel junctions by first-principles calculations, *Phys. Rev. B* **90**, 184409 (2014).

[33] M. Ležaić, Ph. Mavropoulos and S. Blügel, First-principles prediction of high Curie temperature for ferromagnetic bcc-Co and bcc-FeCo alloys and its relevance to tunneling magnetoresistance, *Appl. Phys. Lett.* **90**, 082504 (2007).

[34] B. Dupé, G. Bihlmayer, M. Böttcher, S. Blügel and S. Heinze, Engineering skyrmions in transition-metal multilayers for spintronics, *Nat. Commun.* **7**, 11779 (2016).

[35] See the Supplementary Material at URL for details of the calculation procedures.